



Vortex Domain Walls in Helical Magnets

Fuxiang Li,¹ T. Nattermann,² and V. L. Pokrovsky^{1,3}

¹*Department of Physics, Texas A&M University, College Station, Texas 77843-4242, USA*

²*Institut für Theoretische Physik, Universität zu Köln, D-50937 Köln, Germany*

³*Landau Institute for Theoretical Physics, Chernogolovka, Moscow District, 142432, Russia*

(Received 17 November 2011; published 7 March 2012)

We show that helical magnets exhibit a nontrivial type of domain wall consisting of a regular array of vortex lines, except for a few distinguished orientations. This result follows from topological consideration and is independent of the microscopic models. We used simple models to calculate the shape and energetics of vortex walls in centrosymmetric and noncentrosymmetric crystals. Vortices are strongly anisotropic, deviating from the conventional Berezinskii-Kosterlitz-Thouless form. The width of the domain walls depend only weakly on the magnetic anisotropy, in contrast to ferromagnets and antiferromagnets. We show that vortex walls can be driven by external currents and in multiferroics also by electric fields.

DOI: 10.1103/PhysRevLett.108.107203

PACS numbers: 75.10.-b, 75.60.Ch, 75.70.Kw, 75.85.+t

Introduction.—The structure of domain walls (DWs) determines to a large extent the properties of magnetic materials, in particular, their hardness and switching behavior; it represents an essential ingredient of spintronics [1,2]. Common DWs are of Bloch and Néel types in which the magnetization rotates around a fixed axis, giving rise to a one-dimensional magnetization profile [3,4]. Two-dimensional vortex wall configurations can appear in restricted geometries as a result of the competition of stray field, exchange, and anisotropy energy [1]. The more difficult problem of DWs in helical magnets has not yet been solved.

Here we show that DWs in helical magnets are fundamentally different from Bloch and Néel walls. They are generically characterized by a two-dimensional pattern. For almost all orientations of the DW they contain a regular lattice of vortex singularities. However, DWs of few exceptional orientations, determined by symmetry, are free of vortices and maximally stable. Though DWs do not exist without anisotropy, their width and energy depend only weakly on the anisotropy strength. Similar to other topological defects [5–8], vortex DWs can be driven by electric currents. In multiferroics vortices are electrically charged, allowing manipulation of magnetic DWs by electric fields [9–11].

Helical magnets exhibit a screwlike periodic spin pattern intermediate between ferromagnets and antiferromagnets. Examples of such structures are shown in Fig. 1. In addition to time reversal symmetry, in helical magnets the space inversion symmetry is broken [12], either spontaneously in centrosymmetric crystals, or enforced by the symmetry of the crystalline lattice in noncentrosymmetric crystals. The magnetization \mathbf{m} in these structures rotates around a fixed axis when the coordinate along a fixed direction, generally not coinciding with the rotation axis, changes. Further, we denote the projection of the

magnetization to the rotation axis m_3 , its rotating projection to the perpendicular plane as \mathbf{m}_\perp , and assume that $\mathbf{m}^2 = 1$. The angle of rotation is ϕ .

Centrosymmetric case.—We begin with the centrosymmetric case, since it is simpler and includes already many features discussed in this article. Prominent experimental realizations are frustrated antiferromagnets in rare earth metals Tb, Dy, Ho [13,14], their alloys and compounds RMnO_3 $R \in \{\text{Y, Tb, Dy}\}$ [15], $\text{R}_2\text{Mn}_2\text{O}_5$, $R \in \{\text{Tb, Bi}\}$, as well as $\text{Ni}_3\text{V}_2\text{O}_8$ and LiCu_2O_2 [15,16]. The helical magnetic order originates in these materials from the indirect RKKY exchange which results in a competing nearest neighbor ferromagnetic ($J > 0$) and next nearest neighbor antiferromagnetic ($J' < 0$) interaction along the helical axis [14,17,18]. The corresponding Ginzburg-Landau Hamiltonian then reads [1]

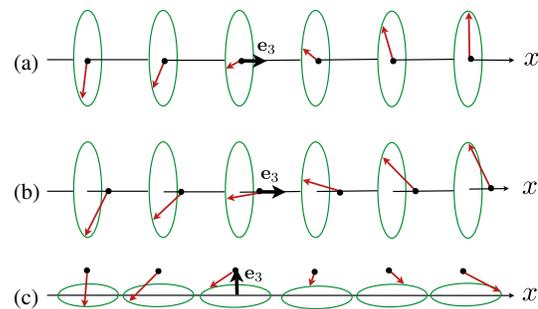


FIG. 1 (color online). Different types of helical ordering. (a) The magnetization rotates in a plane perpendicular to the helical (x) axis as in Tb, Dy, Ho. (b) Conical phase with a nonzero m_3 component of the magnetization as in Ho below 19 K. (c) The magnetization rotates in a plane parallel to the helical axis as in TbMnO_3 .

$$\mathcal{H}_c = \frac{J}{2a} \int_{\mathbf{r}} \left[-\frac{\theta^2}{2} (\partial_x \mathbf{m}_{\perp})^2 + \frac{a^2}{4} (\partial_x^2 \mathbf{m}_{\perp})^2 + (\nabla_{\perp} \mathbf{m})^2 + (\partial_x m_3)^2 + \gamma^2 (m_3^2 + \tau \cos^2 \vartheta_0)^2 \right], \quad (1)$$

where $\int_{\mathbf{r}} = \int d^3r$, $\nabla_{\perp} = \hat{y}\partial_y + \hat{z}\partial_z$, and a is the lattice constant. $\theta = \arccos(J/4|J'|)$ denotes the angle between spins in neighboring layers. The continuum approach is valid for $\theta \ll 1$. θ can be diminished to zero under uniaxial pressure [19]. The last term in (1) is an interpolation that fixes the spins either in-plane, $m_3 = 0$ at $\tau = (T - T_0)/T_0 > 0$, as in Tb, Dy, Ho, and TbMnO₃, or on a cone with angle ϑ_0 for $\tau < 0$, as in Ho below $T_0 = 19$ K [20] ($\vartheta_0 \approx 1.56$ [14]). $\gamma a \approx 0.625$ for Ho and $\gamma a = 0.17$ for Tb [14]. The ground state of (1) has a helical structure with $\phi = qx$:

$$\mathbf{m} = |m_{\perp}|(\mathbf{e}_1 \cos qx + \chi \mathbf{e}_2 \sin qx) + \zeta m_3 \mathbf{e}_3, \quad (2)$$

where $q = \theta/a$ [see Fig. 1(a)]. $\chi = \pm 1$ and $\zeta = \pm 1$ describe the chirality and concavity of the solution, respectively. The rotation axis \mathbf{e}_3 may be parallel to the helical axis $\hat{\mathbf{x}}$, as in Tb, Dy, Ho, or perpendicular to it, as in TbMnO₃ [see Fig. 1(c)]. Because of its space inversion symmetry, (1) is a generic model for any centrosymmetric helical magnet. In centrosymmetric helical magnets where the star of modulation vectors includes 3 vectors, like in CuCrO₂ [11,21], a slightly more complicated model has to be used, but the main conclusions of our analysis remain valid also in this case.

Domain walls and vortices.—DWs separate half spaces with different values of ζ or χ or both. We consider here only walls with different χ since domain walls between phases with different ζ , but the same value of χ , are of Ising-type and well studied. A wall whose normal $\hat{\mathbf{n}}$ is parallel to the helical axis, $\hat{\mathbf{n}} \cdot \hat{\mathbf{x}} = 1$, has been studied by Hubert [1,22]. In such a wall, the derivative of the rotation phase $\partial_x \phi$ changes smoothly from $-q$ to q over a distance $\sim 1/q$ [see Fig. 2(a)]. Its surface tension $\sigma_H \sim (J/a^2)|\theta|^3$

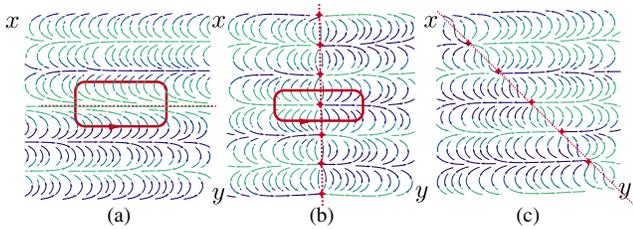


FIG. 2 (color online). DWs in centrosymmetric helical magnets. Cross section parallel to the x - y plane of (a) a Hubert wall, (b) a vortex wall parallel to the helical axis in a system where the magnetization rotates in the x - y plane, (c) a vortex wall tilted with respect to the helical axis. The arrows denote the orientation of \mathbf{m} . For systems where \mathbf{m} is confined to the y - z plane, \mathbf{m} has been rotated by $\pi/2$ for better visibility. The closed (red) contour is described in the text.

is small for small θ . Walls of different orientation were not yet studied theoretically, although seen in experiment, e.g., in Ho by circular polarized x rays [20]. We consider first a wall in the xz plane whose normal $\hat{\mathbf{n}}$ is perpendicular to $\hat{\mathbf{x}}$. Since both domains have the same pitch, the magnetization is periodic along the x axis with the period $2\pi/q$. Circulating counterclockwise along a closed contour \mathcal{C} in the xy plane formed by two horizontal lines at $x = N\pi/q$ and $x = (N + N_v)\pi/q$ with N and N_v being integers and two vertical lines connecting the horizontal ones far from the wall [see the red contour in Fig. 2(b)], an observer sees the change of phase $2\pi N_v$. A similar contour \mathcal{C} enclosing a Hubert wall gives $N_v = 0$. We note that this argument is purely topological and not limited to the particular Hamiltonian (1). In the case of six modulation vectors $\pm \mathbf{q}_i$, $i = 1, 2, 3$, as in CuCrO₂, in addition to the $\pm \mathbf{q}_i$ DWs considered here, also DWs between $\mathbf{q}_i, \mathbf{q}_j$ phases ($i \neq j$) appear, similar to those discussed below for the noncentrosymmetric case.

Vortices are saddle point configurations of the Hamiltonian (1). For $\gamma a \gg 1$ they obey the equation

$$\{4\nabla_{\perp}^2 + a^2[6(\partial_x \phi)^2 - 2q^2 - \partial_x^2] \partial_x^2\} \phi = 0. \quad (3)$$

Vortex lines parallel to $\hat{\mathbf{x}}$ have the standard Kosterlitz-Thouless form [23]. The same applies to vortex lines perpendicular to $\hat{\mathbf{x}}$ on scales much larger than q^{-1} where $(\partial_x \phi)^2 \approx q^2$ and hence Eq. (3) becomes Laplace's equation. On smaller scales, instead of solving (3) exactly, we use a variational ansatz $\phi(\mathbf{r}) = \arctan(\lambda z/x)$, where λ is a variational parameter to be found from the energy minimization. It gives $\lambda^2(r) = \theta^2 + 5/[64 \ln(r/a)]$ where $r^2 = x^2 + \lambda^2 z^2$. The vortex energy per unit length is

$$\varepsilon_v(r) = \frac{\pi J}{a} \ln^{1/2}(r/a) \left[\frac{5}{64} + \theta^2 \ln(r/a) \right]^{1/2}. \quad (4)$$

Equation (4) describes the crossover from the conventional Kosterlitz-Thouless behavior $\sim \ln(r/a)$ at distances $r > r_c = a \exp[5/(64\theta^2)]$ to a $[\ln(r/a)]^{1/2}$ behavior at scales $r < r_c$.

So far we assumed that $\gamma a \gg 1$ and hence the spins are confined at a fixed value of m_3 . However, for $\gamma a < 1$ in the vortex center, i.e., for $r \leq r_v = \gamma^{-1}(1 + \tau \cos^2 \vartheta_0)^{-1} |\ln(\gamma a)|^{1/2}$, spins align parallel to the \mathbf{e}_3 axis to save energy. Thus, $m_3 \zeta = \pm 1$; i.e., the vortex forms a meron [24]. Vortices in the DW have the same vorticity ± 1 and are equidistant with the spacing π/q forming a vortex fence. The energy per unit area of the vortex DW is $\sigma_v = (\sqrt{5}J/4a^2)|\theta| |\ln|\theta||^{1/2} \gg \sigma_H$.

A DW of general orientation with $\hat{\mathbf{n}} \cdot \hat{\mathbf{x}} = \cos \alpha$ consists of a periodic chain of vortices perpendicular to the helical axis and the normal to the DW [Fig. 2(c)]. For α close to 0 the wall can be treated as pieces of Hubert walls separated by vortex steps of the height π/q and length $(\pi/q)/|\tan \alpha|$, giving rise to a vortex staircase. The energy per unit area of such a wall is approximately equal to

$\varepsilon_v[(q \sin \alpha)^{-1}q |\sin \alpha|/\pi + \sigma_H |\cos \alpha|$. At any $\alpha \neq 0$, it is larger than the energy of the Hubert wall.

Noncentrosymmetrics case.—In these systems, invariants violating the space but not time inversion symmetry are permitted. Those terms appear in first order perturbation theory in the spin-orbit coupling constant g [25,26]. Experimental examples of noncentrosymmetric compounds are MnSi [27], $\text{Fe}_{1-x}\text{Co}_x\text{Si}$ [28], and FeGe [29]. The magnetic anisotropy in crystals with cubic symmetry is of the order g^4 . The phenomenological Ginzburg-Landau functional for the magnetization \mathbf{m} has been derived in detail in [30] and takes the form

$$\mathcal{H}_n = \frac{J}{a} \int_{\mathbf{r}} [(\nabla \mathbf{m})^2 + 2g \mathbf{m}(\nabla \times \mathbf{m}) + v \sum_{i=1}^3 m_i^4]. \quad (5)$$

Here we ignored other terms representing the cubic anisotropy since they do not influence our results qualitatively. For $v = 0$ the minimum of energy (5) is given by a planar chiral structure, $\mathbf{m}(\mathbf{r}) = \mathbf{e}_1 \cos \mathbf{q}\mathbf{r} + \mathbf{e}_2 \sin \mathbf{q}\mathbf{r}$, where \mathbf{q} is the wave vector of the helix and \mathbf{e}_1 , $\mathbf{e}_2 = \hat{\mathbf{q}} \times \mathbf{e}_1$, and $\hat{\mathbf{q}}$ form a triad. The direction of \mathbf{q} is arbitrary, but its length $|\mathbf{q}| = g$ is fixed. Contrary to the centrosymmetric helices, states with wave vectors \mathbf{q} and $-\mathbf{q}$ describe the same magnetization reducing the degeneracy space to $SO(3)/Z_2$ [31]. Cubic anisotropy pins the helix direction \mathbf{q} either along one of the cube diagonals or along one of the fourfold axis, depending on the sign of v . DWs separate half spaces with different values of \mathbf{q} . Since $|v| \ll g^2$, one could expect, in analogy with ferromagnets, that the DW locally represents a helical structure whose wave vector slowly rotates pertaining its length constant. We will prove that such a configuration does not exist. Indeed, the generalization of the equation for the magnetization in a structure with slowly varying \mathbf{q} is

$$\mathbf{m}(\mathbf{r}) = \mathbf{e}_1 \cos \phi(\mathbf{r}) + \mathbf{e}_2 \sin \phi(\mathbf{r}), \quad (6)$$

where $\phi(\mathbf{r})$ is an arbitrary function of coordinates. \mathbf{e}_1 , \mathbf{e}_2 , $\nabla \phi$ form a right triad. The requirement of the constancy of the pitch implies $(\nabla \phi)^2 = q^2$, which is the Hamilton-Jacobi equation for a free particle with the boundary conditions $\nabla \phi \rightarrow \mathbf{q}_{1,2}$ at $x \rightarrow \mp \infty$. Since a free particle conserves its momentum, the latter cannot be different in two different asymptotic regions. Thus, it is impossible to construct a DW between two different asymptotic values of the wave vector without changing its modulus between. The DW solution has a width determined by the only existing scale $1/q$ and the surface energy is independent of anisotropy v .

DWs whose plane is a bisector of the asymptotic wave vectors \mathbf{q}_1 and \mathbf{q}_2 do not contain vortices. They are analogs of the Hubert DWs. Their surface tension has the order of magnitude $\sigma \sim Jg/a$. DWs of any different orientation contain a chain of vortex lines for the same reason as in the centrosymmetric case (see Fig. 3, left panel). The vortex lines are located in the plane of the DW

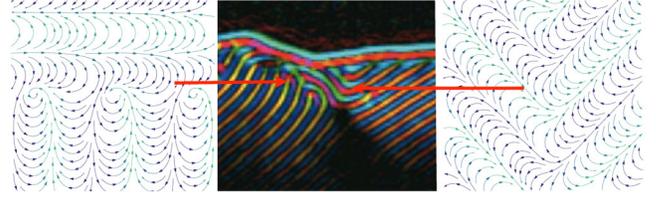


FIG. 3 (color online). DWs in noncentrosymmetric helical magnets. A detail of Fig. 1(g) of Ref. [29] (center) showing two types of DWs in the ferromagnet FeGe; the left one includes vortices, the right one is vortex-free. The panels are theoretically calculated DWs, right without vortices, left with vortices.

perpendicular to the projection of either of the vectors $\mathbf{q}_1 - \mathbf{q}_2 \equiv 2\mathbf{q}_-$ or $\mathbf{q}_1 + \mathbf{q}_2 \equiv 2\mathbf{q}_+$ onto the domain plane depending on what configuration has lower energy. The vortex line spacings in the chain are equal to $\ell_{\pm} = 2\pi/|\hat{\mathbf{n}} \times \mathbf{q}_{\pm}|$. Pictures of both vortex-free and vortex DWs based on variational numerical calculations are shown in Fig. 3, together with the experimental figure of FeGe [29] displaying these structures. For numerical calculations we used (6) and the following ansatz (we write the answer for the first choice of the sign):

$$\phi(\mathbf{r}) = \mathbf{r}\mathbf{q}_+ + \mathbf{n}\mathbf{q}_- w \text{Incosh} \frac{\mathbf{n}\mathbf{r}}{w} + \arctan \frac{\tan \psi_1}{\tanh \psi_2}, \quad (7)$$

where $\psi_1 = [\mathbf{r} - \mathbf{n}(\mathbf{n}\mathbf{r})]\mathbf{q}_-$ and $\psi_2 = |\mathbf{n} \times \mathbf{q}_-| \mathbf{n}\mathbf{r}$. The last term in (7) is the contribution of the vortex array. It has the asymptotics $\pm \psi_1$. The second term does not have any singularity. It corresponds to the vortex-free DW when \mathbf{n} is parallel to $\mathbf{q}_1 - \mathbf{q}_2$, i.e., when the DW plane is the bisector of the vectors \mathbf{q}_1 and \mathbf{q}_2 . Its asymptotics are $\pm(\mathbf{n}\mathbf{r})(\mathbf{n}\mathbf{q}_-)$. The asymptotic of the sum of the second and third terms is $\pm \mathbf{r}\mathbf{q}_-$. Together with the first term they tend asymptotically to $\mathbf{q}_1\mathbf{r}$ above the domain wall and to $\mathbf{q}_2\mathbf{r}$ below. The only variational parameter is w . The surface tension of a vortex DW differs from that of the vortex-free DW by a factor $\sin \beta \ln(1/qa)$, where β is the angle between \mathbf{n} and \mathbf{q}_{\pm} . Apart from a narrow interval of small β , this factor is larger than 1. Because of their higher surface tension, DWs carrying vortices may be unstable with respect to formation of a zigzag structure formed by vortex-free DWs. Zigzag structures observed in experiments with $\text{Fe}_{0.5}\text{Co}_{0.5}\text{Si}$ [28] can be tentatively interpreted as arising from this instability. The zigzag structure is impossible in the helical magnets with uniaxial anisotropy since only one orientation of the vortex-free DWs is allowed. This fact, together with low stability of vortex-carrying DWs, can serve as an explanation of a disordered domain structure observed in Ho [20].

DW roughening.—Roughening of DWs occurs by the formation of terraces which condense at the roughening transition temperature [32]. For Hubert walls, terraces are encircled by vortex rings of some length L . Since their energy and entropy scale as $\varepsilon_v(L)(L/a)$ and L/a ,

respectively, Hubert walls remain asymptotically flat at increasing temperatures, slowing down their propagation. On the contrary, vortex walls are always rough, as seen also experimentally [20].

Driven domain walls.—We assume that the spin of a conduction electron follows adiabatically the magnetization $\mathbf{m}(\mathbf{r})$. This approximation is valid provided $|k_F^\uparrow - k_F^\downarrow| \gg q$. Here k_F^\uparrow is the Fermi momentum of the electrons with spin parallel or antiparallel to \mathbf{m} . Thus, electrons experience a change of angular momentum. Inversely, the electron current \mathbf{j} creates a reaction torque on \mathbf{m} driving the magnetic texture with a force [5–8],

$$F_\alpha = \frac{\hbar}{2e} j_\beta \int_{\mathbf{r}} \{ \mathbf{m} \cdot (\partial_\alpha \mathbf{m} \times \partial_\beta \mathbf{m}) + \beta_{sf} \partial_\beta \mathbf{m} \cdot \partial_\alpha \mathbf{m} \}. \quad (8)$$

The first term is the spin transfer torque [5,6] related to the Berry's curvature $K_\alpha = \epsilon_{\alpha\beta\gamma} \mathbf{m}(\partial_\beta \mathbf{m} \times \partial_\gamma \mathbf{m})$. For a single vortex, its only nonzero component is parallel to the vortex lines and is given by $2\pi m_3 \zeta$. A weak field along the axis of rotation will order ζ of different merons. The force per unit area of the DW exerted by a current of density j parallel to the wall due to the spin torque is of the order $m_3 \zeta \theta (j/10^5 \text{ A m}^{-2}) \text{ N m}^{-2}$. The second term results from the spin relaxation and is orthogonal to the first one. β_{sf} is a dimensionless coefficient which depends on the specific relaxation mechanism [7,8]. The pinning force density due to nonmagnetic impurities of density n_i can be estimated from the theory of collective pinning as $J\theta n_i/6 \approx \theta(T_c/20 \text{ K})(n_i/10^{17} \text{ cm}^{-3}) \text{ N m}^{-2}$, which gives a critical current $j_c \approx 6 \times 10^7 \text{ A m}^{-2}$ for $n_i \approx 10^{19} \text{ cm}^{-3}$.

Multiferroics.—In multiferroics the magnetization can induce the electric polarization [9],

$$\mathbf{P} = \kappa [\mathbf{m}(\nabla \mathbf{m}) - (\mathbf{m} \nabla) \mathbf{m}], \quad (9)$$

where κ is some material constant. \mathbf{P} is only nonzero if $\mathbf{m} \hat{\mathbf{x}} \neq 0$ (as in TbMnO_3). The vortex structure in a helical DW induces a ferroelectric DW, in agreement with experiments [33]. Hubert walls are uncharged whereas vortex lines carry an electric charge $\rho = 2\pi\kappa[\mathbf{e}_3 \times \hat{\mathbf{x}}] \hat{\mathbf{n}}$ per unit length. This allows us to move magnetic DWs by an external electric field.

To conclude, we have shown that DWs both in centrosymmetric and noncentrosymmetric helical magnets consist of a regular array of vortex lines for almost all orientations except of a few that correspond to a minima of the surface energy. The helical DWs are generically two-dimensional textures. They are charged in multiferroics and can be driven by electrical currents and fields.

The authors thank A. Abanov, T. Arima, K. Everschor, M. Kléman, S. Korshunov, N. Nagaosa, A. Rosch, C. Schüssler-Langeheine, G.E. Volovik, P.B. Wiegmann, and M. Zirnbauer for useful discussions and Y. Tokura for the permission to reproduce his experimental figures.

This work has been supported by SFB 608 and by the DOE under Grant No. DE-FG02-06ER 46278.

-
- [1] A. Hubert, *Theorie Der Domänenwände in Geordneten Medien* (Springer, Berlin, 1974).
 - [2] S. S. P. Parkin, M. Hayashi, and L. Thomas, *Science* **320**, 190 (2008).
 - [3] F. Bloch, *Z. Phys.* **74**, 295 (1932).
 - [4] L. Néel, *Ann. Phys. (Paris)* **3**, 137 (1948).
 - [5] A. A. Thiele, *Phys. Rev. Lett.* **30**, 230 (1973).
 - [6] L. Berger, *J. Appl. Phys.* **55**, 1954 (1984).
 - [7] S. Zhang and Z. Li, *Phys. Rev. Lett.* **93**, 127204 (2004).
 - [8] For recent reviews see G. Tatara, H. Kohno, and J. Shibata, *J. Phys. Soc. Jpn.* **77**, 031003 (2008); *Phys. Rep.* **468**, 213 (2008).
 - [9] M. Mostovoy, *Phys. Rev. Lett.* **96**, 067601 (2006).
 - [10] S. Cheong and M. Mostovoy, *Nature Mater.* **6**, 13 (2007).
 - [11] T. Arima, *J. Phys. Soc. Jpn.* **80**, 052001 (2011).
 - [12] M. Kléman, *Philos. Mag.* **22**, 739 (1970).
 - [13] W. C. Koehler, J. W. Cable, M. K. Wilkinson, and E. O. Wollan, *Phys. Rev.* **151**, 414 (1966).
 - [14] J. Jensen and A. R. Mackintosh, *Rare Earth Magnetism Structures and Excitations* (Oxford University Press, New York, 1991).
 - [15] T. Kimura and Y. Tokura, *J. Phys. Condens. Matter* **20**, 434204 (2008).
 - [16] L. C. Chapon *et al.*, *Phys. Rev. Lett.* **93**, 177402 (2004).
 - [17] P. G. De Gennes, *J. Phys. Radium* **23**, 510 (1962).
 - [18] A. B. Harris, in *The Handbook of Magnetism and Advanced Magnetic Materials*, edited by H. Kronmüller and S. Parkin (Wiley, New York, 2006).
 - [19] A. V. Andrianov, D. I. Kosarev, and A. I. Beskrovnyi, *Phys. Rev. B* **62**, 13844 (2000).
 - [20] J. C. Lang, D. R. Lee, D. Haskel, and G. Srajeret, *J. Appl. Phys.* **95**, 6537 (2004).
 - [21] M. Frontzek *et al.*, *J. Phys. Condens. Matter* **24**, 016004 (2012).
 - [22] P. I. Melnichuk, A. N. Bogdanova, U. K. Röbber, and K.-H. Müller, *J. Magn. Magn. Mater.* **248**, 142 (2002).
 - [23] J. M. Kosterlitz and D. J. Thouless, *J. Phys. C* **6**, 1181 (1973).
 - [24] T. Senthil *et al.*, *Science* **303**, 1490 (2004).
 - [25] I. E. Dzyaloshinsky, *J. Phys. Chem. Solids* **4**, 241 (1958).
 - [26] T. Moriya, *Phys. Rev.* **120**, 91 (1960).
 - [27] S. M. Mühlbauer *et al.*, *Nature (London)* **427**, 227 (2004).
 - [28] M. Uchida, Y. Onose, Y. Matsui, and Y. Tokura, *Science* **311**, 359 (2006).
 - [29] M. Uchida *et al.*, *Phys. Rev. B* **77**, 184402 (2008).
 - [30] K.-Y. Ho, T. R. Kirkpatrick, Y. Sang, and D. Belitz, *Phys. Rev. B* **82**, 134427 (2010).
 - [31] G. E. Volovik and V. P. Mineev, *Sov. Phys. JETP* **45**, 1186 (1977).
 - [32] P. Nozière, in *Solids Far from Equilibrium*, edited by C. Godrèche (Cambridge University Press, New York, 1992).
 - [33] M. Fiebig *et al.*, *Nature (London)* **419**, 818 (2002).